

Restorative Dentistry Issue (Removable Prosthodontics, Fixed Prosthodontics, Endodontics, Dental Biomaterials, Operative Dentistry)

4-1-2023

Effect of Aging Treatments on Properties of Zirconia with Different Levels of Translucency

Mayar Abdel El-Salam

Dentist at Al-Zahraa University Hospital, Cairo, Egypt., mirasamir3333@gmail.com

Sahar Abdel-Aziz

Professor of Crowns and Bridges department, Faculty of Dental Medicine For Girls, Al-Azhar University, Cairo, Egypt., sahar_abdelwahab@yahoo.com

Zahraa Gabal

Lecturer of Crowns and Bridges department, Faculty of Dental Medicine for Girls, Al-Azhar University, Cairo, Egypt., zahraagabal.26@azhar.edu.eg

Follow this and additional works at: <https://azjd.researchcommons.org/journal>



Part of the [Other Dentistry Commons](#)

How to Cite This Article

Abdel El-Salam, Mayar; Abdel-Aziz, Sahar; and Gabal, Zahraa (2023) "Effect of Aging Treatments on Properties of Zirconia with Different Levels of Translucency," *Al-Azhar Journal of Dentistry*. Vol. 10: Iss. 2, Article 15.

DOI: <https://doi.org/10.58675/2974-4164.1502>

This Original Study is brought to you for free and open access by Al-Azhar Journal of Dentistry. It has been accepted for inclusion in Al-Azhar Journal of Dentistry by an authorized editor of Al-Azhar Journal of Dentistry. For more information, please contact yasmeenmahdy@yahoo.com.



Effect of Aging Treatments on Properties of Zirconia with Different Levels of Translucency

Mayar S. Abdel El-Salam^{1*}, Sahar A. Abdel-Aziz^{2*}, Zahraa A. Gabal^{3*}

Codex : 1-10/23.04

azhardentj@azhar.edu.eg

http://adjg.journals.ekb.eg

https://doi.org/10.58675/2974-4164.1502

Restorative Dentistry
(Removable Prosthodontics, Fixed
Prosthodontics, Endodontics, Dental
Biomaterials, Operative Dentistry)

ABSTRACT

Purpose: The aim of this study was to evaluate the effect of low-temperature degradation (L-TD), and weathering process on translucency, surface roughness, biaxial-flexural strength, and crystalline phase identification of zirconia with different levels of translucency. **Materials and methods:** A total of ninety-six (N= 96) zirconia discs were fabricated in this study. Samples were divided into three groups (n=32 each) according to type of zirconia: IPS EmaxZirCAD of low, medium translucency and Incoris translucent Zirconia of high translucency. Translucency measurements, surface roughness, biaxial flexural strength determination and phase identification were carried out before and after aging. Each group was then sub-divided into 2 subgroups (n=16); (subgroup A): Low-temperature degradation (L-TD) at 134°C, (subgroup B): Accelerated aging by means of a weathering process (WP). **Results:** Statistical analysis using two-way ANOVA test revealed that there was a significant effect on translucency parameter (TP), and L-TD showed statistically significantly higher mean TP than WP. L-TD showed significantly lower mean roughness than WP. There was no significant difference between biaxial flexural strength values before aging and after L-TD and WP. There was no phase transformation identified before and after aging indicating resistance to different types of artificial aging. **Conclusions:** Low-temperature degradation and weathering process affect translucency parameter and surface roughness of zirconia-based materials. Artificial aging doesn't affect the biaxial flexural strength, and phase identification of different zirconia translucencies.

KEYWORDS

Translucency, surface roughness,
zirconia, degradation,
weathering process.

INTRODUCTION

Dental ceramic restorations have been used for decades in dental prostheses such as crowns and fixed dental prostheses⁽¹⁾, as a consequence of their exceptional cosmetic appearance and

1. Dentist at Al-Zahraa University Hospital, Cairo, Egypt.

2. Professor of Crowns and Bridges department, Faculty of Dental Medicine For Girls, Al-Azhar University, Cairo, Egypt.

3. Lecturer of Crowns and Bridges department, Faculty of Dental Medicine for Girls, Al-Azhar University, Cairo, Egypt.

* Corresponding author email: mirasamir3333@gmail.com

biocompatibility properties. It has been shown that this kind of dental biomaterial provided the most precise mimicry of color, translucency, and texturing of human dentition ⁽²⁾.

A well-known type of dental ceramics is the multi-phase Zirconia, which can occur in three distinct crystallo-graphic phases based on the degree of temperature (i.e., mono-clinic, tetragonal, and cubic). A tetragonal phase structure of zirconia is asserted at room temperature, when yettriaoxide [Y_2O_3] is added as a stabilizing-oxide, despite the fact that the thermodynamically preferred state is the monoclinic one ⁽³⁾.

The transformation toughening mechanism is responsible for the higher fracture toughness, hardness, and flexural strength of yettria-stabilized tetragonal zirconia polycrystalline. It has been revealed that during the application of stresses, a four percent positive volumetric change (expansion) occurs as a consequence of phase transformation from the tetragonal form to the monoclinic one resulting in internal compressive stresses that partly guarding the tip of the crack from the external stress and hence, cause prevention of crack propagation ⁽⁴⁾.

Additives, method of processing, and grain size and distribution, are all considered controlling factors of zirconia translucency. Enhancing the grain size and distributing the grains eventually and homogenously, not only can improve the translucency of zirconia through minimizing the interface between grains and decreasing porosity, but also gives exceptional strength ⁽⁵⁾.

There are different grades of 3-YTZP that show some degree of light transmittance. In order to improve the translucency of this material for esthetics the concentration of alumina additive should be decreased, porosity should be eliminated and by increasing the yettria content ⁽⁶⁾.

The most translucent 5-YTZP materials were indicated for anterior crowns and fixed dental

prosthesis. It is formed by increasing the yettria content from three mol. % to five mol. %, this will increase the cubic phases that reduce the light scattering defect producing high translucency ⁽⁷⁾.

Artificial accelerated aging or low-temperature degradation (LTD) is a way that can imitate natural conditions allowing the difference in color of ceramic restorations throughout the course of time to be detected. It's worth mentioning that surface roughness compromises the esthetic and biomechanical properties of dental prostheses resulting in accelerated aging ⁽⁸⁾.

Clinical behavior and shortcoming of dental ceramics can be expected from its mechanical properties including strength as a prime feature. As detected by X-Ray Diffraction (XRD), phase transformation from tetragonal to monoclinic phase induced by stresses, greatly improves mechanical properties of ZrO_2 -containing ceramics ⁽⁹⁾.

Low-temperature degradation was identified to occur as a result of unprompted phase transformation from the tetragonal to the monoclinic phase, occurring gradually by time at low-thermal and presence of water thus it is triggered on the surface of the ceramics. This type of transformation may reduce flexural strength of certain types of zirconia and induce changes in optical features of high translucent-zirconia after aging treatment⁽¹⁰⁾.

The mechanism by which crystalline, mechanical, and optical stability of zirconia-based dental materials work together, can give a prospective guideline for the implementation of translucent zirconia for clinical recommendation ⁽¹⁰⁾.

The null hypotheses proposed for the present study were that artificial aging will not affect translucency, flexural strength, surface roughness, and crystalline phase identification of yettria stabilized zirconia.

MATERIALS AND METHODS

Sample size and grouping:

Calculating sample size was performed using interventional study (randomized controlled study) taking into consideration the following based on the results of a previous study ⁽⁶⁾, confidence level 0.95%, alpha (α) error 0.05 (5%), beta (β) error 0.1 (10%) i.e. power of the study 0.9 (90%) calculated; the resultant sample size (N) calculated to be (96) samples. The samples were divided to three groups (n=32 each) according to material with different level of translucency:

Group I : IpsEmaxZirCAD of low translucency (n=32).

Group II: IpsEmaxZirCAD of medium translucency(n=32).

Group III : Incorlis translucent Zirconia of high translucency(n=32).

Each group was divided into two subgroups (n=16) according to process of aging:

Subgroup A: Low-temperature degradation (L-TD).

Subgroup B: Accelerated aging (weathering process) (WP).

The study design and methodology was approved by the Research Ethics Committee of the Faculty of Dental Medicine for Girls, Al-Azhar University, with the code REC-CR-22-07.

Preparation of samples:

Zirconia blanks were milled in the form of cylinders of 12mm diameter using CAD/CAM Core Tec model 250 in dry milling machine (Eiterfeld, Germany) , according to the design imported (cylinder shape). To compensate for the expected shrinkage during sintering, the blanks were milled with larger dimensions (20-25% larger than the desired final size).

A total of ninety-six (N=96) discs with 12 mm diameter and 1.8 mm thick were cut from the cylinders via a precision cutting device isomet 4000 micro saw (Buehler Germany), under 2,500 revolutions per minute through a disc of diamond 0.6 mm thick, under a cooling system. The ratio of water coolant to anticorrosive agent was [30:1].

To compensate for the expected reduction in size that occurred after the sintering process, samples were cut 20:25 % greater than the required final size. it was measured by a digital caliper. Partially sintered disc samples were fully sintered following the manufacturer's guidelines at the center of the TABEO sintering furnace, (TABEO-1/M/ ZIRKON-100, Mihmvoigt, Germany), high-temperature furnace with program control unit on sintering beads, fig. (1). The digital caliper was also used in determining the dimensions of samples following the sintering process. The planned final dimensions of each sample were 10 mm in diameter and 1.5mm in thickness.

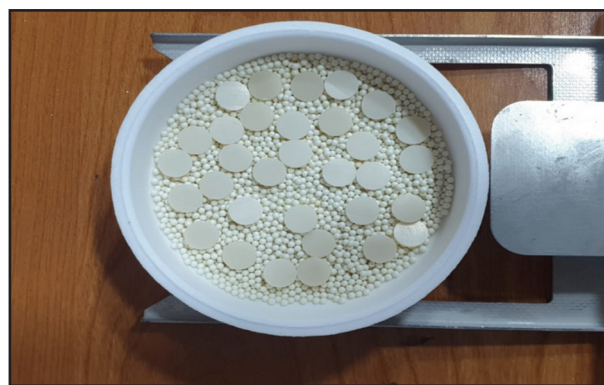


Figure (1) Sintering boats with samples placed over sintering beads

After the samples have been sintered, once it was cooled to room temperature, minimal finishing was carried out according to the manufacturer's recommendations; using diamond finishing stone at low speed using low pressure avoiding local phase transition, twice on each surface in one direction. Polishing was carried out using KENDA finishing and polishing kit (Vaduz, Liechtenstein) without

using polishing paste following manufacturer recommendations.

Low-temperature degradation of the samples:

Samples of subgroup (A) were low-temperature degraded using an autoclave (TS-Tau sterile autoclave, FinoMoransco-COMO, Italy). The samples were packed independently in sterilization pack and arranged on autoclave trays and were placed in the autoclave for 1 hour, 134°C, and 0.2 MPa pressure.

Experimental time intervals were calculated after the temperature of the autoclave reached 134°C. Samples were stored after cooling to room temperature in a glass air-tight container till testing.

Weathering process:

An accelerated weathering tester (Q.U.V Dongguan, Guangdong, China) was used to expose the samples of subgroup (B) to an artificial accelerated aging process through weathering cycles. Samples were put in a chamber that was previously programmed to 25 cycles for 300 hours. A controlled irradiance of ultraviolet lamps that emits light at 340 nm wavelength, was used to subject each sample from only one surface to intermittent cycles of light and darkness (i.e., The test cycle was 8 hours of ultraviolet exposure at 50°C, 4 hour of condensation exposure at 40°C plus water spray). The whole weathering procedure was done under 450 KJ/m² of energy.

Testing Procedures:

Samples of the three groups were tested before and after aging:

Translucency Parameter (TP value):

The translucency was determined and recorded through a reflecting spectrophotometer (Model RM200QC, X-Rite, Neu-Isenburg, Germany) with a standard previously fixed aperture size (4 mm). Specimens were placed in the middle of aperture for the two backings.

Surface Roughness procedure:

Specimens were photographed using a USB Digital microscope with a built-in camera (U500X Capture Digital Microscope, Guangdong, China) attached to a computer.

Biaxial flexural strength (MPa):

A test for measuring the biaxial flexural strength by using (uniform compression on a disc) with a ball on a ring fixture was selected ⁽¹¹⁾. The test was utilized at a crosshead speed of one millimeter with a computer-controlled materials testing machine (Model 3345; Instron Industrial Products, Norwood, MA, USA). A five-kilo newton load cell was utilized for test measurements and eventually, all the recorded data was generated and saved via a digital software (Instron® Bluehill Lite Software). Discs were placed on 8-mm diameter circular knife-edge support with a 3.8 mm diameter rounded indenter loaded in the middle.

The unpolished surface of each disc was selected to be the loaded side whereas the polished surface was selected to be the tension side. A thin film of rubber was positioned in between the load applier tip and the sample surface. Higher fracture stress results in more elastic energy being temporarily retained before being released during fracture, producing more fragments.

Crystalline phase identification

The samples were examined to test their amorphous nature using Philips Analytical X-Ray diffraction system, PHILIPS X-Ray Diffractometer (Caerphilly, United Kingdom). The generator tension was 40KV and the generator current was 30mA. Analyses were performed on samples having a fixed surface area dimension of 1.54 Cm² both after and before aging. There were using the phases of the Rietveld refinement to index and analyze tetragonal zirconia, monoclinic zirconia, t-ZrO₂, cubic zirconia, c-ZrO₂ and m-ZrO₂. Each detected

phase's Y₂O₃ content was determined using the percentage of tetragonal of the t-ZrO₂ in relation to revised lattice parameters phase, quantified by the proportion $c/2a$.

Statistical analysis:

Mean and standard deviation values were used as representatives for the data and study results. Intergroup evaluations and comparisons were done using Two Way ANOVA test. Boneferroni post-hoc test was used for pairwise comparison when ANOVA test was found to be significant. IBM SPSS software program was used to perform the statistical analysis of the current study (IBM SPSS Statistics for Windows, Ver. 23.0.0, Armonk, NY, IBM Corporation).

RESULTS

Translucency parameter (TP) values before and after aging, table (1), and figure (2):

With low translucency zirconia after L-TD; there was a statistically significant increase in mean TP after aging. After WP; there was a statistically significant decrease in mean TP after aging.

With medium translucency zirconia after L-TD; there was a statistically significant increase in mean TP after aging. After WP; there was a statistically significant decrease in mean TP after aging.

With high translucency zirconia after L-TD; there was a statistically significant increase in mean TP after aging. After WP; there was a statistically significant decrease in mean TP after aging.

Table (1) Repeated measures ANOVA results of comparison of TP values before and after aging.

Zirconia translucency	Aging process	Before aging		After aging		<i>p-value</i>	Effect size
		Mean	SD	Mean	SD		
Low translucency	L-TD	8.43	2.14	10.03	2.53	0.041*	0.049
	WP	7.82	1.94	3.21	0.98	<0.001*	0.299
Medium translucency	L-TD	9.53	2.05	12.45	3.9	<0.001*	0.147
	WP	8.04	1	4.18	1.67	<0.001*	0.23
High translucency	L-TD	11.38	1.77	13.51	3.28	0.007*	0.083
	WP	10.21	1.85	3.9	1.86	<0.001*	0.445

*: Significant at $P \leq 0.05$ SD = Standard deviation, P = probability, * non-significant at $p > 0.05$

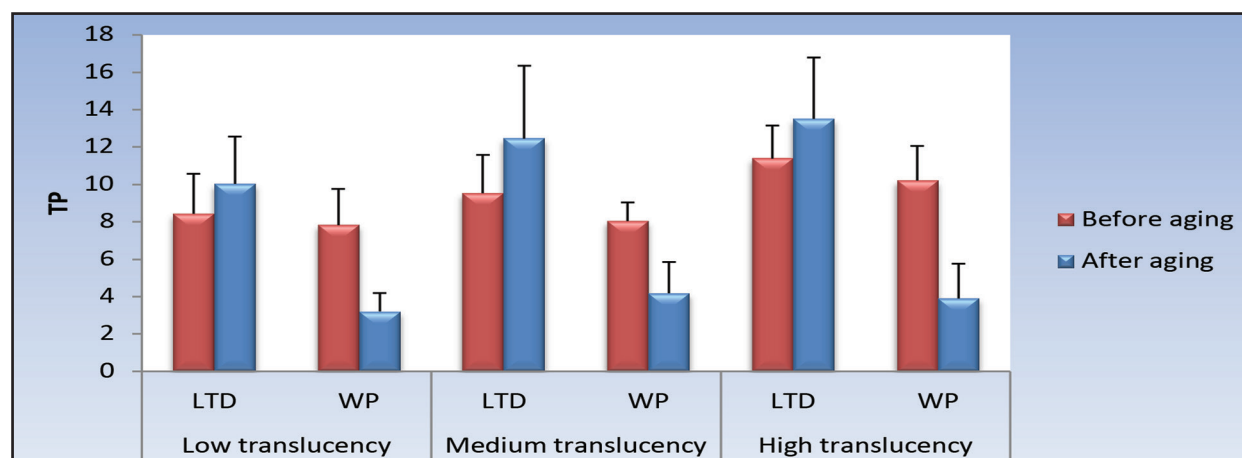


Figure (2): Bar chart illustrating results of comparison of TP measurements represented as mean and standard deviations before and after aging

Surface roughness values before and after aging, table (2), and figure (3):

With low translucency zirconia whether after L-TD or WP; there was a statistically significant increase in mean Ra after aging.

With medium translucency zirconia after L-TD;

there was no statistically significant change in mean Ra after aging. After WP; there was a statistically significant increase in mean Ra after aging.

With high translucency zirconia whether after L-TD or WP; there was no statistically significant change in mean Ra after aging.

Table (2) Repeated measures ANOVA results of comparison of between Ra (μm) values before and after aging.

Zirconia translucency	Aging process	Before aging		After aging		p-value	Effect size
		Mean	SD	Mean	SD		
Low translucency	L-TD	0.2893	0.0008	0.2924	0.0043	<0.001*	0.144
	WP	0.2897	0.0013	0.2924	0.0026	0.002*	0.11
Medium translucency	L-TD	0.2898	0.0014	0.2907	0.0037	0.303	0.013
	WP	0.2904	0.0019	0.2925	0.0031	0.014*	0.069
High translucency	L-TD	0.289	0.0016	0.2884	0.0023	0.482	0.006
	WP	0.29	0.0012	0.2917	0.0019	0.051	0.044

*: Significant at $P \leq 0.05$ SD = Standard deviation, P= probability, * non-significant at $p > 0.05$

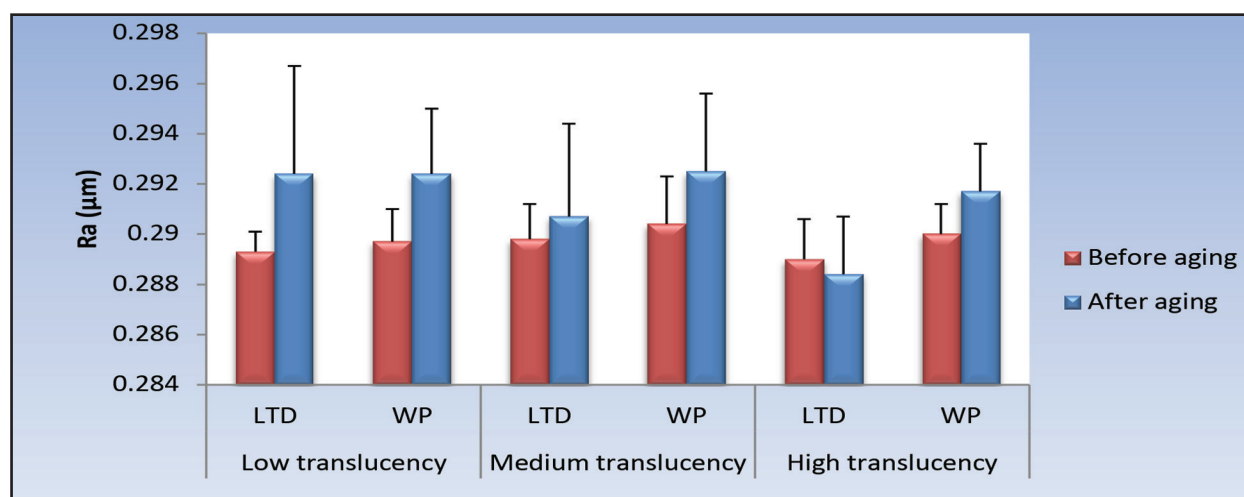


Figure (3): Bar chart illustrating results of comparison of Ra measurements represented as mean and standard deviations before and after aging

Biaxial flexural strength values, table (3), and figure (4):

Whether with low, medium as well as high translucent zirconia; there was no statistically significant difference between biaxial flexural strength values without aging, after L-TD as well as after WP.

Crystalline phase identification values, , table (4), and figure (5):

The quantitative phase analysis of translucent zirconia whether low, medium as well as high; didn't reveal a measurable phase transformation by XRD after L-TD as well as after WP.

Table (3) Two way ANOVA results of comparison of between biaxial flexural strength (MPa) values with different interactions of variables

Aging process	Low translucency		Medium translucency		High translucency		P-value	Effect size (Partial eta squared)
	Mean	SD	Mean	SD	Mean	SD		
No aging	1318.9	57.8	980.4	66.4	1106.6	212.2	0.074	0.135
L-TD	1080.2	288.8	1168.1	189.6	1106.2	84	0.823	0.011
WP	1086.7	251.2	841.2	157.7	1161.1	449.8	0.082	0.13
P-value	0.184		0.090		0.909			
Effect size (Partial eta squared)	0.09		0.125		0.005			

*: Significant at $P \leq 0.05$ SD = Standard deviation, P= probability, * non-significant at $p > 0.05$

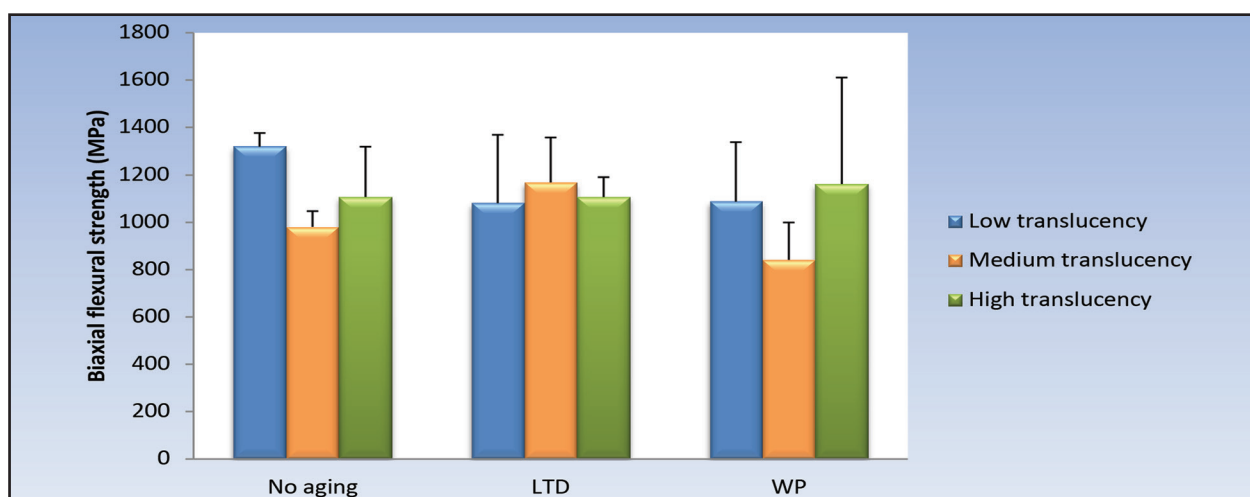


Figure (4): Bar chart illustrating results of comparison of biaxial flexural strength measurements represented as mean and standard deviations before and after aging

Table (4) Percentage of tetragonal zirconium oxide for with different interactions of variables before and after aging.

Zirconia translucency	Aging process	Before aging		After aging	
		YO ₂ oxide	t-ZrO ₂	YO ₂	t-ZrO ₂
Low translucency	L-TD	67%	33%	65.2%	36%
	WP			69%	31%
Medium translucency	L-TD	72%	25%	73%	27%
	WP			74.2%	24%
High translucency	L-TD	75.9%	28%	78%	27%
	WP			76%	26.2%

*: Percentage% of YO₂:Yttrium oxide , t-ZrO₂: tetragonal zirconium oxide

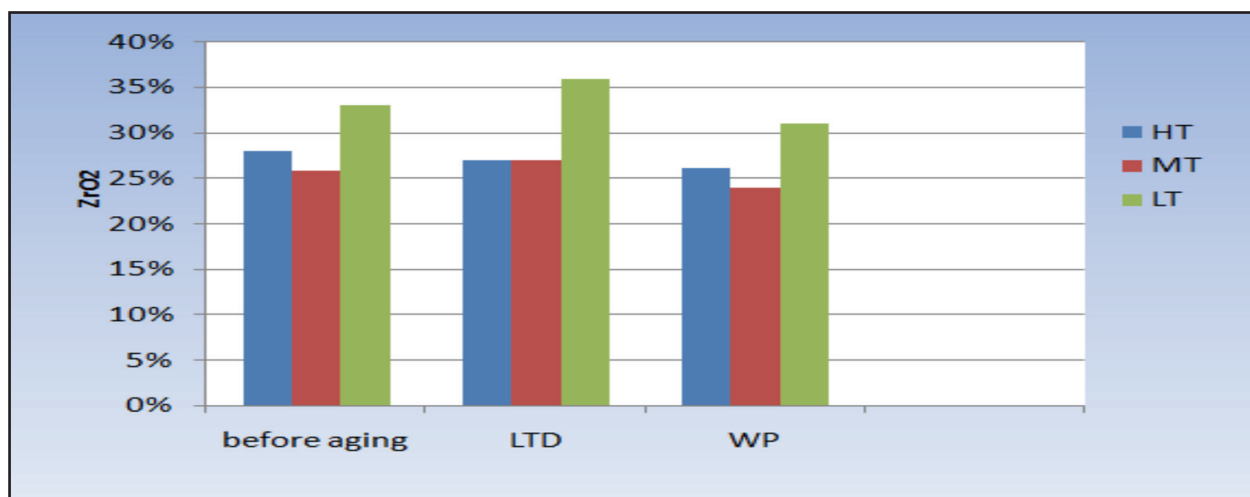


Figure (5): Bar chart representing percentage of zirconium oxide and amount of phase transformation before and after aging

DISCUSSION

Dental prostheses made up of dental ceramics are well known for their inherent esthetics, wear resistance, and biocompatibility⁽¹²⁾. Zirconia dental ceramics are used for restoration of posterior teeth, as these oral regions are subjected to high forces of mastication, a condition that highlights the need for an inherently tough and strong dental ceramic like yettria-stabilized tetragonal zirconia (YTZ). However, its opaque nature limits its use in esthetic area due to low optical properties^(13,14).

Low temperature degradation, which is usually known as aging, is a condition that when occurs under humidity can result in loss of YTZ strength and other advantageous features. It was suggested that detrimental crystal transformation damages the microstructure which enriches YTZ ceramics with the excellent features throughout its fabrication procedures. Hence, it is essential to understand the phenomenon when selecting a dental restorative material⁽¹⁵⁾.

Therefore, the present study aimed to evaluate the effect of low-temperature degradation and ac-

celerated aging (weathering process) on translucency, surface roughness, biaxial flexural strength and crystalline phase identification of zirconia-based dental ceramics with various translucency levels.

Zirconia with various translucency levels were used in this study including IpsEmaxZirCAD of low translucency, IpsEmaxZirCAD of medium translucency and Incoriss translucent Zirconia of high translucency.

Zirconia blocks were cut using a precision cutting machine (isomet 4000 micro-saw). The samples were sectioned 20-25% greater than the required size to compensate for the expected reduction in dimension.

Sintering of samples were done following the manufacturer's instructions at high temperature furnace at 1460-1530°C to produce impenetrable structures confirming unity between the zirconia grains and to avoid larger grain formation.

Constructed samples were finished and polished to mimic real clinical conditions because it has been claimed that different finishing techniques have a significant impact on zirconia's mechanical properties⁽¹⁶⁾. Both procedures were carried out according to the manufacturer recommendations; using diamond finishing stone at low speed using low pressure avoiding local phase transition, twice on each surface in one direction.

Several studies have recommended autoclaving as an established method for accelerating the aging of YTZ materials as it causes low-temperature degradation (L-TD)⁽¹⁷⁾. In the present study, aging in an autoclave for 1 hour at 134°C was done for samples in (subgroup A). The aging procedure followed simulate approximately 1 year of clinical use⁽¹⁸⁾.

Artificial accelerated aging through weathering process is an experimental method used to mimic oral environmental conditions extra-orally⁽¹⁹⁾. Samples in (subgroup B) were subjected to 300 hour of artificial aging using a weathering process in an accelerated weathering tester which simulates 1 year clinically⁽²⁰⁾.

In the current study, it was hypothesized that artificial aging will not affect translucency, surface roughness, biaxial flexural strength and crystalline phase identification of yttria stabilized zirconia. However, the null hypothesis was partially rejected as the results showed that artificial aging has a significant effect on translucency, surface roughness but have no effect on biaxial flexural strength and crystalline phase identification of yttria stabilized zirconia.

The results in the present study illustrated that the effect of L-TD aging regardless of zirconia translucency, showed that there was a statistically significant increase in TP mean after aging. Those results were in agreement with a previous study⁽²¹⁾ in which a statistically significant increase after artificial aging can be attributed to the increase in grain size of the materials therefore increase in the light transmission. Also agreed with another study⁽²²⁾ in which translucency increased with increasing aging time for zirconia attributed to reduced dispersion of light from cubic zirconia's grain boundaries.

Another study⁽²³⁾ concluded that increasing the aging time results in more translucency of conventional zirconia and more opacity of multilayered one.

These findings were contraindicated with the results reached by a previous study⁽²⁴⁾ in which mean translucent parameter value before aging showed statistically significantly higher value than after aging and contrast ratio before aging showed statistically significantly lower value than after aging. This could be explained due to transformation from tetragonal to monoclinic phase with associated surface roughness which caused an increase in light scattering.

On the other hand, the effect of WP aging regardless of zirconia translucency, showed that there was a statistically significant decrease in TP mean after aging. The results were in agreement with another study⁽²⁵⁾ concluded that light scattering

from pores, and the difference in refractive indices between tetragonal and monoclinic zirconia crystals would cause the translucency to decrease.

The results were also in agreement with another study ⁽²⁶⁾, which showed a proportional increase of opacity with the increase in diameter thickness, residual porosities, and grain boundaries. All these factors result in more scattering of incident light and hence the translucency of ceramic is diminished.

On the other hand, these findings were in contradiction with the results reached by another study ⁽²⁷⁾ in which the translucency didn't decrease after aging in the tested type of zirconia which is probably associated with the decrease in the amount of transformation of zirconia and this is followed by decreased superficial irregularity, light scattering, and reflection.

Regarding the surface roughness, there was a statistically significant increase in surface roughness after aging (L-TD& WP) with low and medium translucency as showed in the current study. The finding was in consistent with previous study ⁽²⁸⁾ which found that surface roughness of the zirconia increased after being exposed to hydrothermal aging at low-temperature when aging procedure performed in an autoclave at 122°C at 2 bars for 8hours.

On the contrary with the present study findings, another study ⁽²⁹⁾ concluded that aging did not promote any relevant surface change. They explained that through the fact that samples were mirror polished, thus after LTD samples might retain its polishing surface. This aging schedule was carried out very quickly as a result to that, it may not lead to pull-out of grain, leading to identical roughness esteems to the non-aged zirconia. However, this finding agreed with the present study in which the low-temperature degradation and weathering process did not affect the surface roughness of high translucent zirconia.

The results were in agreement with a previous study ⁽²⁰⁾ which revealed that artificial aging affects

surface roughness of Lava ultimate ceramic but does not affect surface roughness of high translucent zirconia.

The results were also in agreement with another study ⁽²³⁾ who stated that the aging process significantly elevated the roughness (Ra) measurements values in all tested groups. However, the Ra values of that study were in the range of 0.003 and 0.01 μm which is much lesser than Ra value of 0.2 μm , so it is expected to be acceptable clinically.

On the other hand, results obtained disagree with those of a another previous study ⁽³⁰⁾ which stated that aging doesn't affect surface roughness of YTZ ceramics. The reason may be attributed to the different autoclave durations and different methods of specimen preparation.

Regarding biaxial flexural strength, there was insignificant effect on flexural strength which could be noticed in the results. The finding was in consistent with previous study ⁽³¹⁾ in which zirconia materials did not show any sign of discernible change in flexural strength after artificial aging although a quantity of greater than 40% of monoclinic phase has been found. This could be clarified by that transformation zone has no extremely sufficient extension within material to impact its main part strength.

On the contrary of the findings in the present study, another study ⁽³²⁾ concluded that flexural strength decreased by aging due to presence of internal defects in which the monoclinic phase entered at the surface and phase transformation continued throughout into the majority of the ceramic.

Regarding the crystalline phase identification, various groups of zirconia exhibited distinguishable crystalline form, chemical structure, and microstructural features. All materials have highly polished surface and significant degree of compaction with uniformly distributed boundaries of internal grains together with less than one percentage of remnant porosity ⁽³³⁾.

The results in this study didn't reveal any detectable phase transformation suggesting reluctance

to hydrothermal degradation. This is in agreement with previous study⁽³⁰⁾ which revealed a direct proportional relationship between the amount of yttria in dental Zirconia of high translucency and its resistance to accelerated aging.

In agreement with the current study, a previous study⁽³⁴⁾ which suggested that no monoclinic phase noticed following the process of aging due to high amount of cubic crystal retard the aging degradation in which phase transformation didn't happen.

Besides, results obtained disagree with another study⁽³⁵⁾ which reported that degradation starts on the surface with a quick transition from a tetragonal to a monoclinic phase and stabilizes after 26 hours. In comparison to highly translucency zirconia, conventional zirconia displayed a greater level of surface deterioration.

CONCLUSIONS

The following can be concluded from the present study:

1. Low-temperature degradation and weathering process have a significant effect on translucency parameter of zirconia with different levels of translucency.
2. Low-temperature degradation and weathering process have a significant effect on surface roughness of low, medium translucent zirconia, and have no effect on surface roughness of high translucent zirconia.
3. Low-temperature degradation, and weathering process didn't affect the flexural strength and phase identification of zirconia-based materials.

ACKNOWLEDGMENT

I would like to express my deep gratitude and thanks to Allah, who provided me with unlimited help to get this work done. I would also like to express my deepest thanks and respect to Dr Mohammed Abbas Professor of Dental Materials,

Faculty of Dental Medicine for boys, Al-Azhar University for his guidance and input throughout the process of this research and especially for his patience, caring and support.

RECOMMENDATIONS

Clinically relevant restorations and different prosthetic designs should be investigated rather than the disc shaped samples

FUNDING

The authors declare that this scientific piece of work didn't receive any funding support from any party.

CONFLICT OF INTEREST

There is no conflict of interest.

REFERENCES

1. Ispas Ana, Losif L, Daniela P, Negucioiu M, Constantiniuc M, Bacali M, et al. Comparative Assessment of the functional parameters for metal- ceramic and all-ceramic teeth restorations in prosthetic dentistry-a literature review. *Biology (Basel)* 2022; 11:1-15.
2. Elbadry M, Mohsen C, Hashem R. Effect of different shading techniques on the color of zirconia ceramic restoration (an in vivo study). *J MediSci* 2022; 10: 372-9.
3. Kirejczyk MS, Chmura K, Gronkiewicz K, Gala A, Loster JE, Ryniewicz W. Adhesive cementation of zirconia-based ceramics-surface modification methods literature review. *Coatings* 2022; 12:1-11.
4. Mirt T, Abram A, Velde NV, Jeran I, Bermejo R, Kocjan A. Effect of airborne-particle abrasion of yttria-containing zirconia dental ceramics on mechanical properties before and after regeneration firing. *J Euro Cermic Society* 2022; 42:5035-44.
5. NistorL, Gradinaro M, Rica R, Marasescu P, Stan M, Manolea H, et al. :Zirconia Use in Dentistry-Manufacturing and Properties. *Curr Health Sci J* 2019;45:28-35.
6. Zhang F, Reveron H, Spies BC, Meerbeek BV, Chevalier J: Trade-off between fracture resistance and translucency of zirconia and lithium-disilicate glass ceramics for monolithic restorations. *ActaBiomatr* 2019;91:24-34.

7. Seghi R R, Rio DLD: Biomaterial Ceramic and Adhesive Technology. Dent Clinic of North America 2019;63:233-48.
8. Abbasimoghaddam S, Hakimaneh SMR, Hooshmand T, Shayegh SS. Effects of aging on mechanical and optical properties of translucent and opaque zirconia. J Iran Dent Assoc 2021; 33: 22-32.
9. Kulyk V, Duriagina Z, Vasylyv B, Vavruk V, Kovbasiuk T, Lyutyty P. The effect of sintering temperature on the phase composition, microstructure, and mechanical properties of yttria-stabilized zirconia. Mater 2022; 15:1-17.
10. Nakamura K, Tarkeshi A, Niklasson A, Shishido S, Svanborg P, Barkarmo S, et al. Influence of crystalline phase transformation induced by airborne-particle abrasion and low-temperature degradation on mechanical properties of dental zirconia ceramics stabilized with over 5 mol% yttria. J Mech Behav Biomed Mater 2022; 125: 1-12.
11. Turker HT. Effect of size on biaxial flexural strength for cement-based materials by using a triangular plate method. Front Struct Civ Eng. 2022; 16:1017-28.
12. Zhang Y, Lawn BR. Evaluating dental zirconia. Dent Mater. 2019; 35: 15–23.
13. Kim BK, Yun JH, Jung WK, Lim CH, Zhang Y, Kim DK. Mitigating grain growth in fully stabilized zirconia via a two-step sintering strategy for esthetic dental restorations. Inter J Appl Ceram Tech 2022; 1-13.
14. Galindo CH, Gorrita MR, Solano SM, Figallo MAS, Lagares DT. A review on CAD/CAM yttria-stabilized tetragonal zirconia polycrystal (YTZ) and polymethyl methacrylate (PMMA) and their biological behavior. Polymers (Basel). 2022; 14:1-8.
15. Rabel K, Nold J, Pehlke D, Shen J, Abram A, Kocjan A, et al. Zirconia fixed dental prostheses fabricated by 3D gel deposition show higher fracture strength than conventionally milled counterparts. J Mech Behav Biomed Mater. 2022 ;135:1-12.
16. De Carvalho IHG, Da Silva NR, Vila-Nova TEL, De Almeida LFD, Verissimo AH, De Melo RM, et al. Effect of finishing/polishing techniques and aging on topography, *C. albicans* adherence, and flexural strength of ultra-translucent zirconia: an in situ study. Clin Oral Invest 2022; 26: 889-900.
17. Prado PHCO, Dapievek S, Campos TMB, Valandrol F, De Melo RM. Effect of hydrothermal and mechanical aging on the fatigue performance of high-translucency zirconias. Dent Mater 2022; 38:1060-71.
18. Perrichon A, Reynard B, Gremillard L, Chevalier J, Farizon F, Geringer J. A testing protocol combining shocks, hydrothermal aging and friction, applied to zirconia toughened alumina (ZTA) hip implants. J Mech Behav Biomed Mater. 2017;65: 600-8.
19. Lee SM, Choi YS. Effect of ceramic material and resin cement systems on the color stability of laminate veneers after accelerated aging. J prosth dent. 2018; 120: 99-106.
20. Hamza TA, Alameldin AA, Elkouedi AY, Wee AG. Effect of artificial accelerated aging on surface roughness and color stability of different ceramic restorations. Stomatological Dis Sci. 2017; 1: 8-13
21. Kanpalt B, Burdugroglu D, Kara O. Effect of artificial aging on the translucency of monolithic zirconia materials sintered at different temperatures. J Prosth Dent 2022; 128: 91-6.
22. Kim HK, Kim SH. Effect of hydrothermal aging on the optical properties of precolored dental monolithic zirconia ceramics. J Proth Dent. 2019; 121:676-82.
23. Choi YS, Kang KH, Att W. Effect of aging process on some properties of conventional and multilayered translucent zirconia for monolithic restorations. Ceramics Inter. 2020; 46: 1854–68.
24. Alghazzawi TF. The effect of extended aging on the optical properties of different zirconia materials. J Prosthodont Res. 2017; 61:305-14.
25. Fathy SM, El-Fallal AA, El Negoly SA. Translucency of monolithic and core zirconia after hydrothermal aging. Acta Biomater Odontol Scand. 2015; 1:86-92.
26. Zhang CY, Agingu C, Tsoi JKH, Yu H. Effects of aging on the color and translucency of monolithic translucent YTZ ceramics: A systematic review and meta-analysis of in vitro studies. Biomed Research Inter. 2021; 10: 1-10.
27. Lucas TJ, Lawson NC, Jenanowski GM, Burgess JO. Phase transformation of dental zirconia following artificial aging. J Biomed Mater Res. 2015;103:1519–23.
28. Peampring C, Kengtanyakich S. Surface roughness and translucency of various translucent zirconia ceramics after hydrothermal aging. Eur J Dent. 2021;1:1-7
29. Amaral M, Weitzel ISSL, Silvestri T, Guilardi LF, Pereira GKR, Valandro LF. Effect of grinding and aging on subcritical crack growth of a YTZ ceramic. J Braz Oral Res. 2018; 32:1-9.
30. Yang H, Xu YL, Hong G, Yu H. Effects of low-temperature degradation on the surface roughness of yttria-stabilized tetragonal zirconia polycrystal ceramics: A systematic review and meta-analysis. J Prosth Dent. 2021; 125: 222-30.

31. Wille S, Zumstrull P, Kaidas V, Jessen LK, Kern M. Low-temperature degradation of single layers of multilayered zirconia in comparison to conventional unshaded zirconia: Phase transformation and flexural strength. *J mechan Behav Biomater*. 2018; 77:171-5.
32. Zhuang Y, Zhu Z, Jiao T, Sun J. Effect of aging time and thickness on low-temperature degradation of dental zirconia. *J Prosth*. 2018; 28: 404-10.
33. Amarante JEV, Pereira MVS, De Souza GM, Alves MFRP, Simba BG, Dos Santos C. Effect of hydrothermal aging on the properties of zirconia with different levels of translucency. *J Mech Behav Biomed Mater*. 2020; 109:1-13.
34. Kengtanyakich S, Peampring C. An experimental study on hydrothermal degradation of cubic-containing translucent zirconia. *J Adv Prosthodont*. 2020; 12: 265-72.
35. Oliveira ALN, Elias CN, Dos Santos HES, Dos Santos C, De Biasi S. Physical properties and color stainability by coffee and red wine of opaque and high translucency zirconia dental ceramics after hydrothermal degradation. *Inter J Biomater*. 2022; 1: 1-11.